National foreword

This British Standard is the official English language version of EN 755-9:2001. Together with the standards listed in the following table, it supersedes BS 1474:1987, BS 4300-4:1973, BS 4300-12:1969 and BS 4300-15:1973 which are withdrawn

This part of BS EN 755 is published together with:

— BS EN 12020-1, *Aluminium and aluminium alloys — Extruded precision profiles in alloys EN AW-6060 and EN AW-6063 — Part 1: Technical conditions for inspection and* delivery;

— BS EN 12020-2, *Aluminium and aluminium alloys — Extruded precision profiles in alloys EN AW-6060 and EN AW-6063 — Part 2: Tolerances on dimensions and form.*

The following table gives the full list of implemented European Standards which supersede the British Standards

Superseded British Standards	Superseding European Standards
BS 1474:1987:	BS EN 515:1993, BS EN 573-3:1995, BS EN 573-4:1995, BS EN 755-1:1997, BS EN 755-2:1997, BS EN 755-3:1996, BS EN 755-4:1996, BS EN 755-5:1996, BS EN 755-6:1996, BS EN 755-7:1998, BS EN 755-8:1998, BS EN 755-9:2001, BS EN 12020-1:2001, BS EN 12020-2:2001
BS 4300-4:1973:	BS EN 515:1993, BS EN 573-3:1995, BS EN 573-4:1995, BS EN 755-1:1997, BS EN 755-2:1997, BS EN 755-3:1996, BS EN 755-4:1996, BS EN 755-5:1996, BS EN 755-6:1996, BS EN 755-9:2001
BS 4300-12:1969:	BS EN 515:1993, BS EN 573-3:1995, BS EN 573-4:1995, BS EN 755-1:1997, BS EN 755-2:1997, BS EN 755-3:1996, BS EN 755-4:1996, BS EN 755-5:1996, BS EN 755-6:1996, BS EN 755-7:1998, BS EN 755-8:1998, BS EN 755-9:2001
BS 4300-15:1973:	BS EN 515:1993, BS EN 573-3:1995, BS EN 573-4:1995, BS EN 755-1:1997, BS EN 755-2:1997, BS EN 755-3:1996, BS EN 755-4:1996, BS EN 755-5:1996, BS EN 755-6:1996, BS EN 755-7:1998, BS EN 755-8:1998, BS EN 755-9:2001

This British Standard, having been prepared under the direction of the Engineering Sector Committee, was published under the authority of the Standards Committee and comes into effect on 15 June 2001

Amendments issued since publication

Amd. No.	Date	Comments
13301 Corrigendum No. 1	July 2001	Correction of supersession details in national foreword

© BSI 07-2001

ISBN 0 580 37046 1

EUROPEAN STANDARD

NORME EUROPÉENNE

EUROPÄISCHE NORM

EN 755-9

April 2001

ICS 77.150.10

English version

Aluminium and aluminium alloys - Extruded rod/bar, tube and profiles - Part 9: Profiles, tolerances on dimensions and form

Aluminium et alliages d'aluminium - Barres, tubes et profilés filés - Partie 9: Profilés, tolérances sur dimension et forme

Aluminium und Aluminiumlegierungen - Stranggepresste Stangen, Rohre und Profile - Teil 9: Profile, Grenzabmaße und Formtoleranzen

This European Standard was approved by CEN on 18 February 2001.

CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration. Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the Management Centre or to any CEN member.

This European Standard exists in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the Management Centre has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Czech Republic, Denmark, Finland, France, Germany, Greece, Iceland, Ireland, Italy, Luxembourg, Netherlands, Norway, Portugal, Spain, Sweden, Switzerland and United Kingdom.



EUROPEAN COMMITTEE FOR STANDARDIZATION
COMITÉ EUROPÉEN DE NORMALISATION
EUROPÄISCHES KOMITEE FÜR NORMUNG

Management Centre: rue de Stassart, 36 B-1050 Brussels

© 2001 CEN All rights of exploitation in any form and by any means reserved worldwide for CEN national Members.

Ref. No. EN 755-9:2001 E

The UK participation in its preparation was entrusted by Technical Committee NFE/35, Light metals and their alloys, to Subcommittee NFE/35/5, Wrought aluminium and aluminium alloys, which has the responsibility to:

- aid enquirers to understand the text;
- present to the responsible European committee any enquiries on the interpretation, or proposals for change, and keep the UK interests informed;
- monitor related international and European developments and promulgate them in the UK.

A list of organizations represented on this subcommittee can be obtained on request to its secretary.

Cross-references

The British Standards which implement international or European publications referred to in this document may be found in the BSI Standards Catalogue under the section entitled "International Standards Correspondence Index", or by using the "Find" facility of the BSI Standards Electronic Catalogue.

A British Standard does not purport to include all the necessary provisions of a contract. Users of British Standards are responsible for their correct application.

Compliance with a British Standard does not of itself confer immunity from legal obligations.

Summary of pages

This document comprises a front cover, an inside front cover, pages i and ii, the EN title page, pages 2 to 18, an inside back cover and a back cover.

The BSI copyright date displayed in this document indicates when the document was last issued.

© BSI 06-2001

BRITISH STANDARD

BS EN
755-9:2001
Incorporating
Corrigendum No. 1

Aluminium and aluminium alloys — Extruded rod/bar, tube and profiles —

Part 9: Profiles, tolerances on dimensions and form

The European Standard EN 755-9:2001 has the status of a British Standard

ICS 77.150.10

NO COPYING WITHOUT BSI PERMISSION EXCEPT AS PERMITTED BY COPYRIGHT LAW

BSI — British Standards Institution

BSI is the independent national body responsible for preparing British Standards. It presents the UK view on standards in Europe and at the international level. It is incorporated by Royal Charter.

Revisions

British Standards are updated by amendment or revision. Users of British Standards should make sure that they possess the latest amendments or editions.

It is the constant aim of BSI to improve the quality of our products and services. We would be grateful if anyone finding an inaccuracy or ambiguity while using this British Standard would inform the Secretary of the technical committee responsible, the identity of which can be found on the inside front cover. Tel: 020 8996 9000. Fax: 020 8996 7400.

BSI offers members an individual updating service called PLUS which ensures that subscribers automatically receive the latest editions of standards.

Buying standards

Orders for all BSI, international and foreign standards publications should be addressed to Customer Services. Tel: 020 8996 9001. Fax: 020 8996 7001. Standards are also available from the BSI website at http://www.bsi-global.com.

In response to orders for international standards, it is BSI policy to supply the BSI implementation of those that have been published as British Standards, unless otherwise requested.

Information on standards

BSI provides a wide range of information on national, European and international standards through its Library and its Technical Help to Exporters Service. Various BSI electronic information services are also available which give details on all its products and services. Contact the Information Centre. Tel: 020 8996 7111. Fax: 020 8996 7048.

Subscribing members of BSI are kept up to date with standards developments and receive substantial discounts on the purchase price of standards. For details of these and other benefits contact Membership Administration. Tel: 020 8996 7002. Fax: 020 8996 7001. Further information about BSI is available on the BSI website at http://www.bsi-global.com.

Copyright

Copyright subsists in all BSI publications. BSI also holds the copyright, in the UK, of the publications of the international standardization bodies. Except as permitted under the Copyright, Designs and Patents Act 1988 no extract may be reproduced, stored in a retrieval system or transmitted in any form or by any means – electronic, photocopying, recording or otherwise – without prior written permission from BSI.

This does not preclude the free use, in the course of implementing the standard, of necessary details such as symbols, and size, type or grade designations. If these details are to be used for any other purpose than implementation then the prior written permission of BSI must be obtained.

If permission is granted, the terms may include royalty payments or a licensing agreement. Details and advice can be obtained from the Copyright Manager. Tel: 020 8996 7070.

BSI
389 Chiswick High Road
London
W4 4AL

Contents

Foreword 3

1 Scope 4

2 Alloy groups 4

3 Tolerances on dimensions 5
3.1 Cross-sectional dimensions 5
3.2 Length 12
3.3 Squareness of cut ends 12

4 Tolerances on form 12
4.1 General 12
4.2 Straightness 12
4.3 Convexity - Concavity 13
4.4 Contour 14
4.5 Twist 15
4.6 Angularity 17
4.7 Corner and fillet radii 18

Foreword

This European Standard has been prepared by Technical Committee CEN/TC 132 "Aluminium and aluminium alloys", the secretariat of which is held by AFNOR.

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by October 2001, and conflicting national standards shall be withdrawn at the latest by October 2001.

Within its programme of work, Technical Committee CEN/TC 132 entrusted CEN/TC 132/WG 5 "Extruded and drawn products" to prepare the following standard :

EN 755-9, *Aluminium and aluminium alloys- Extruded rod/bar, tube and profiles - Part 9 : Profiles, tolerances on dimensions and form.*

This standard is part of a set of nine standards. The other standards deal with :

EN 755-1, *Aluminium and aluminium alloys - Extruded rod/bar, tube and profiles - Part 1 : Technical conditions for inspection and delivery.*

EN 755-2, *Aluminium and aluminium alloys - Extruded rod/bar, tube and profiles - Part 2 : Mechanical properties.*

EN 755-3, *Aluminium and aluminium alloys - Extruded rod/bar, tube and profiles - Part 3 : Round bars, tolerances on dimensions and form.*

EN 755-4, *Aluminium and aluminium alloys - Extruded rod/bar, tube and profiles - Part 4 : Square bars, tolerances on dimensions and form.*

EN 755-5, *Aluminium and aluminium alloys - Extruded rod/bar, tube and profiles - Part 5 : Rectangular bars, tolerances on dimensions and form.*

EN 755-6, *Aluminium and aluminium alloys - Extruded rod/bar, tube and profiles - Part 6 : Hexagonal bars, tolerances on dimensions and form.*

EN 755-7, *Aluminium and aluminium alloys - Extruded rod/bar, tube and profiles - Part 7 : Seamless tubes, tolerances on dimensions and form.*

EN 755-8, *Aluminium and aluminium alloys - Extruded rod/bar, tube and profiles - Part 8 : Porthole tubes, tolerances on dimensions and form.*

According to the CEN/CENELEC Internal Regulations, the national standards organizations of the following countries are bound to implement this European Standard: Austria, Belgium, Czech Republic, Denmark, Finland, France, Germany, Greece, Iceland, Ireland, Italy, Luxembourg, Netherlands, Norway, Portugal, Spain, Sweden, Switzerland and the United Kingdom.

1 Scope

This part of EN 755 specifies the tolerances on dimensions and form for aluminium and aluminium alloy extruded profile with a cross section contained within a circumscribing circle not greater than 800 mm (see Figure 1).

This standard applies to extruded profiles for general engineering applications only.

The tolerances in this standard only apply to those dimensions that can be physically measured.

NOTE Some of the products listed in the present standard can be subject to patent or patent applications, and their listing herein does not in any way imply the granting of a licence under such patent right.

CEN/TC 132 affirms it is its policy that in the case when a patentee refuses to grant licences on standardised standard products under reasonable and not discriminatory conditions, then this product shall be removed from the corresponding standard.

Dimensions in millimetres

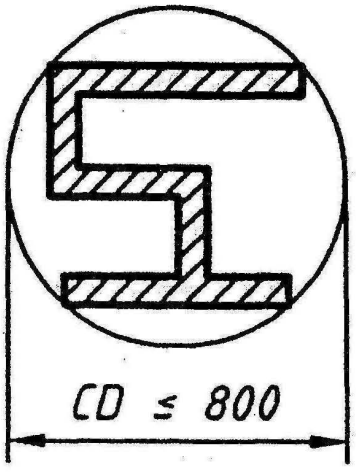


Figure 1 — Circumscribing circle

2 Alloy groups

For the purpose of this European Standard, the alloys are distributed into two groups which correspond to varying degrees of difficulty when manufacturing the products.

The division into group I and group II of the most commonly used general engineering alloys is specified in table 1. Grouping of other alloys is subject to agreement between purchaser and supplier.

Table 1 — Alloy groups

Group I	EN AW-1050A, EN AW-1070A, EN AW-1200, EN AW-1350 EN AW-3003, EN AW-3103 EN AW-5005, EN AW-5005A EN AW-6101A, EN AW-6101B, EN AW-6005, EN AW-6005A, EN AW-6106, EN AW 6008, EN AW-6060, EN AW-6063, EN AW-6063A, EN AW-6463
Group II	EN AW-2007, EN AW-2011, EN AW-2011A, EN AW-2014, EN AW-2014A, EN AW-2017A, EN AW-2024, EN AW-2030 EN AW-5019[a], EN AW-5051A, EN AW-5251, EN AW-5052, EN AW-5154A, EN AW-5454, EN AW-5754, EN AW-5083, EN AW-5086 EN AW-6012, EN AW-6018, EN AW-6351, EN AW-6061, EN AW-6261, EN AW-6262, EN AW-6081, EN AW-6082 EN AW-7003, EN AW-7005, EN AW-7020, EN AW-7022, EN AW-7049A, EN AW-7075

[a] EN AW-5019 is the new designation for EN AW-5056A.

3 Tolerances on dimensions

3.1 Cross-sectional dimensions

3.1.1 General

The tolerances on the dimensions listed below (see Figure 2) are specified in the relevant Tables 2 to 8.

A : wall thicknesses except those enclosing the hollow spaces in hollow profiles ;

B : wall thicknesses enclosing the hollow spaces in hollow profiles except those between two hollow spaces ;

C : wall thicknesses between two hollow spaces in hollow profiles ;

E : the length of the shorter leg of profiles with open ends ;

1 : all dimensions except wall thickness.

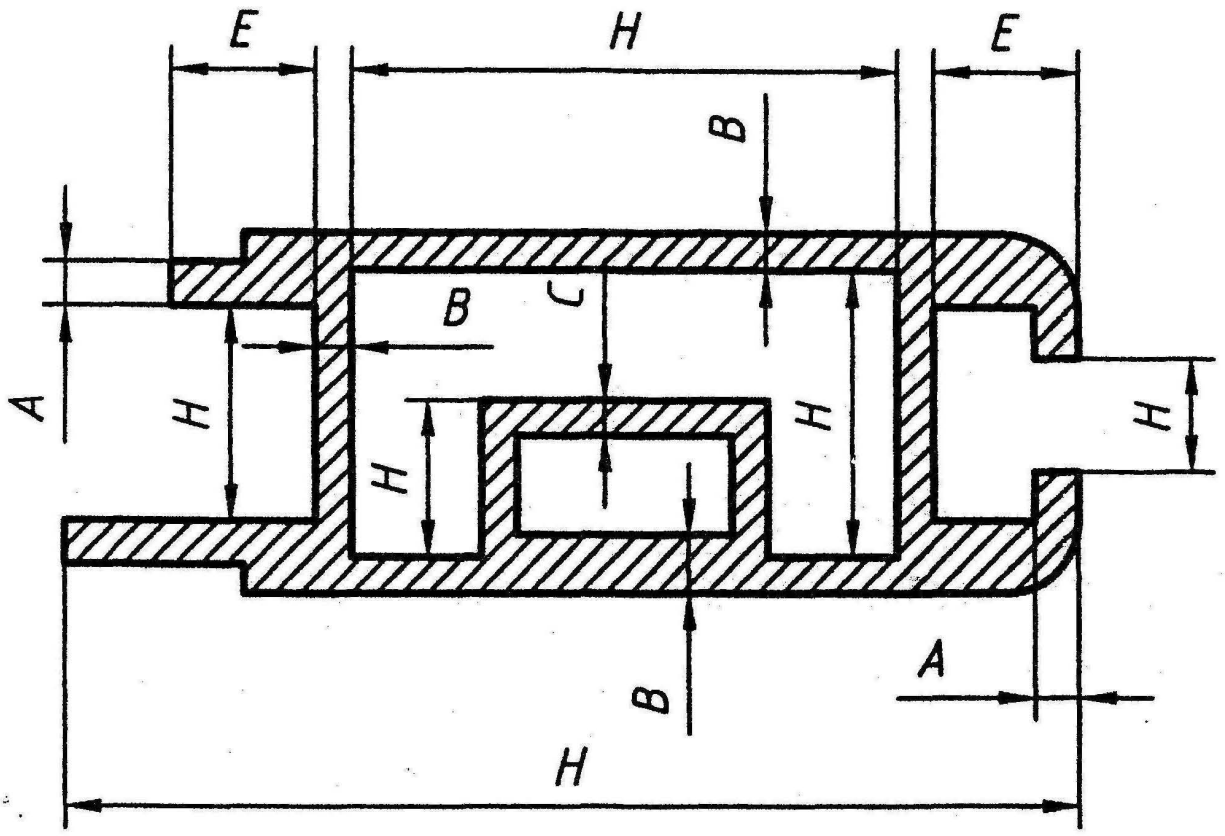


Figure 2 — Definition of dimensions *A*, *B*, *C*, *E*, *H*

3.1.2 Tolerances on dimensions other than wall thickness

The tolerances on dimensions shall be as specified in Tables 2 and 3. For profiles with open ends (see Figures 3, 4 and the relevant examples) the tolerances specified in Table 4 shall be added to those of Tables 2 and 3 for dimension *H* across open ended legs in order to obtain the tolerances on the gap between any opposite points on these ends.

Table 2 — Tolerances on cross-sectional dimensions of solid and hollow profiles - Alloy group I

Dimensions in millimetres

Dimension H		Tolerances on H for circumscribing circle CD [a] [b]				
Over	Up to and including	$CD \leq 100$	$100 < CD \leq 200$	$200 < CD \leq 300$	$300 < CD \leq 500$	$500 < CD \leq 800$
-	10	± 0,25	± 0,30	± 0,35	± 0,40	± 0,50
10	25	± 0,30	± 0,40	± 0,50	± 0,60	± 0,70
25	50	± 0,50	± 0,60	± 0,80	± 0,90	± 1,0
50	100	± 0,70	± 0,90	± 1,1	± 1,3	± 1,5
100	150	-	± 1,1	± 1,3	± 1,5	± 1,7
150	200	-	± 1,3	± 1,5	± 1,8	± 2,0
200	300	-	-	± 1,7	± 2,1	± 2,4
300	450	-	-	-	± 2,8	± 3,0
450	600	-	-	-	± 3,8	± 4,2
600	800	-	-	-	-	± 5,0

a These tolerances do not apply to tempers O and Tx510. For these tempers, the tolerances shall be subject to agreement between the supplier and the purchaser.

b For profiles with open ends, see Figures 3 and 4, the tolerances for H in the area of the open ends shall be increased by the values specified in Table 4.

Table 3 — Tolerances on cross-sectional dimensions of solid and hollow profiles - Alloy group II

Dimensions in millimetres

Dimension H		Tolerances on H for circumscribing circle CD [a] [b]				
Over	Up to and including	$CD \leq 100$	$100 < CD \leq 200$	$200 < CD \leq 300$	$300 < CD \leq 500$	$500 < CD \leq 800$
-	10	± 0,40	± 0,50	± 0,55	± 0,60	± 0,70
10	25	± 0,50	± 0,70	± 0,80	± 0,90	± 1,1
25	50	± 0,80	± 0,90	± 1,0	± 1,2	± 1,3
50	100	± 1,0	± 1,2	± 1,3	± 1,6	± 1,8
100	150	-	± 1,5	± 1,7	± 1,8	± 2,0
150	200	-	± 1,9	± 2,2	± 2,4	± 2,7
200	300	-	-	± 2,5	± 2,8	± 3,1
300	450	-	-	-	± 3,5	± 3,8
450	600	-	-	-	± 4,5	± 5,0
600	800	-	-	-	-	± 6,0

a These tolerances do not apply to tempers O and Tx510. For these tempers, the tolerances shall be subject to agreement between the supplier and the purchaser.

b For profiles with open ends, see Figures 3 and 4, the tolerances for H in the area of the open ends shall be increased by the values specified in Table 4.

Table 4 — Additions to the tolerances on cross-sectional dimensions *H* of solid and hollow profiles with open ends - Alloy groups I and II

Dimensions in millimetres

Dimension *E*		Additions to the tolerances on *H* in Tables 2 and 3 for dimensions across the ends of open ended profiles
Over	Up to and including	
-	20	-
20	30	± 0,15
30	40	± 0,25
40	60	± 0,40
60	80	± 0,50
80	100	± 0,60
100	125	± 0,80
125	150	± 1,0
150	180	± 1,2
180	210	± 1,4
210	250	± 1,6
250	-	± 1,8

Figures 3 and 4 below show open ends on hollow and solid profiles. The determination of tolerances on cross-sectional dimensions *H* is shown in the following calculation examples 1 and 2.

Examples of tolerance calculations across open ended profiles.

EXAMPLE 1

Dimension *H* : 20 mm

Dimension *E* : 100 mm

Circumscribing circle *CD* 100 mm to 200 mm

Alloy group I

The tolerance on *H* according to Table 2 is ± 0,40 mm ; plus the additional tolerance according to Table 4 which is ± 0,60 mm ; total tolerance on *H* is ± 1,0 mm.

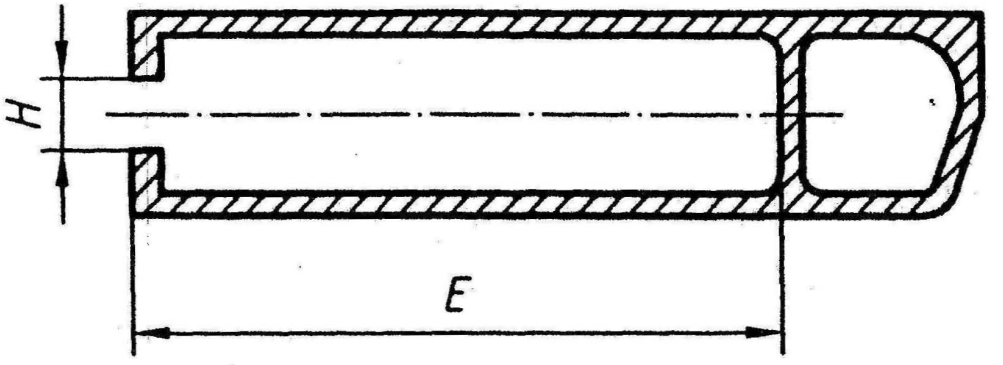


Figure 3 — Hollow profile with open end

EXAMPLE 2

Dimension H : 40 mm

Dimension E : 50 mm

Circumscribing circle CD 100 mm to 200 mm

Alloy group II

The tolerance on H according to Table 3 is ± 0,90 mm ; plus the additional tolerance according to Table 4 which is ± 0,40 mm ; total tolerance on H is ± 1,3 mm.

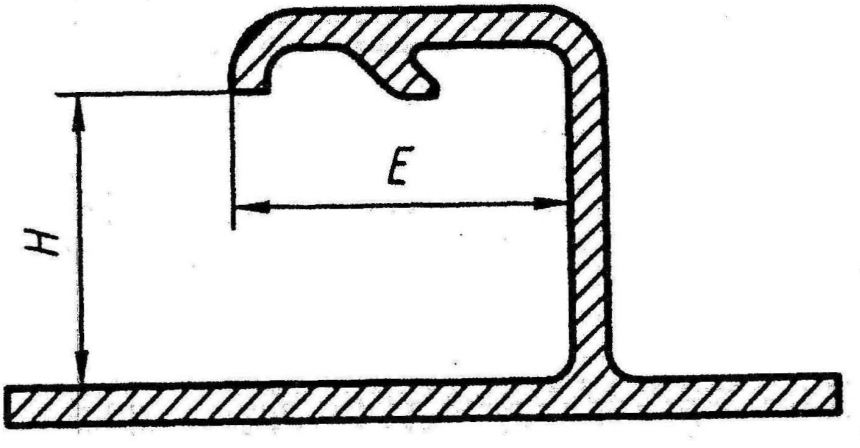


Figure 4 — Solid profile with open end

3.1.3 Tolerances on wall thickness of solid and hollow profiles

The tolerances on wall thickness of solid and hollow profiles shall be specified in Tables 5, 6, 7 and 8.

Table 5 — Tolerances on wall thickness for profiles with a circumscribing circle up to and including 300 mm - Alloy group I

Dimensions in millimetres

Nominal wall thickness *A*, *B* or *C*		Tolerances on wall thickness					
		Wall thickness *A* Circumscribing circle		Wall thickness *B* [a] Circumscribing circle		Wall thickness *C* Circumscribing circle	
Over	Up to and including	$CD \leq 100$	$100 < CD \leq 300$	$CD \leq 100$	$100 < CD \leq 300$	$CD \leq 100$	$100 < CD \leq 300$
-	1,5	± 0,15	± 0,20	± 0,20	± 0,30	± 0,25	± 0,35
1,5	3	± 0,15	± 0,25	± 0,25	± 0,40	± 0,30	± 0,50
3	6	± 0,20	± 0,30	± 0,40	± 0,60	± 0,50	± 0,75
6	10	± 0,25	± 0,35	± 0,60	± 0,80	± 0,75	± 1,0
10	15	± 0,30	± 0,40	± 0,80	± 1,0	± 1,0	± 1,2
15	20	± 0,35	± 0,45	± 1,2	± 1,5	± 1,5	± 1,9
20	30	± 0,40	± 0,50	± 1,5	± 1,8	± 1,9	± 2,2
30	40	± 0,45	± 0,60	-	± 2,0	-	± 2,5
40	50	-	± 0,70	-	-	-	-

[a] For seamless hollow profiles the tolerances given for wall thickness *C* shall apply.

Table 6 — Tolerances on wall thickness for profiles with a circumscribing circle over 300 mm – Alloy group I

Dimensions in millimetres

Nominal wall thickness *A*, *B* or *C*		Tolerances on wall thickness					
		Wall thickness *A* Circumscribing circle		Wall thickness *B* [a] Circumscribing circle		Wall thickness *C* Circumscribing circle	
Over	Up to and including	$300 < CD \leq 500$	$500 < CD \leq 800$	$300 < CD \leq 500$	$500 < CD \leq 800$	$300 < CD \leq 500$	$500 < CD \leq 800$
-	1,5	± 0,25	-	-	-	-	-
1,5	3	± 0,35	± 0,40	± 0,60	± 0,80	± 0,75	± 1,0
3	6	± 0,40	± 0,50	± 0,80	± 1,0	± 1,0	± 1,2
6	10	± 0,45	± 0,55	± 1,0	± 1,2	± 1,2	± 1,5
10	15	± 0,50	± 0,60	± 1,2	± 1,5	± 1,5	± 1,9
15	20	± 0,55	± 0,65	± 1,7	± 2,0	± 2,0	± 2,5
20	30	± 0,60	± 0,70	± 2,0	± 2,5	± 2,5	± 3,0
30	40	± 0,70	± 0,80	± 2,2	± 2,7	± 2,7	± 3,3
40	50	± 0,80	± 0,90	-	-	-	-

[a] For seamless hollow profiles the tolerances given for wall thickness *C* shall apply.

Table 7 — Tolerances on wall thickness for profiles with a circumscribing circle up to and including 300 mm - Alloy group II

Dimensions in millimetres

Nominal wall thickness *A*, *B* or *C*		Tolerances on wall thickness					
		Wall thickness *A* Circumscribing circle		Wall thickness *B* [a] Circumscribing circle		Wall thickness *C* Circumscribing circle	
Over	Up to and including	$CD \leq 100$	$100 < CD \leq 300$	$CD \leq 100$	$100 < CD \leq 300$	$CD \leq 100$	$100 < CD \leq 300$
-	1,5	± 0,20	± 0,25	± 0,30	± 0,40	± 0,35	± 0,50
1,5	3	± 0,25	± 0,30	± 0,35	± 0,50	± 0,45	± 0,65
3	6	± 0,30	± 0,35	± 0,55	± 0,70	± 0,60	± 0,90
6	10	± 0,35	± 0,45	± 0,75	± 1,0	± 1,0	± 1,3
10	15	± 0,40	± 0,50	± 1,0	± 1,3	± 1,3	± 1,7
15	20	± 0,45	± 0,55	± 1,5	± 1,8	± 1,9	± 2,2
20	30	± 0,50	± 0,60	± 1,8	± 2,2	± 2,2	± 2,7
30	40	± 0,60	± 0,70	-	± 2,5	-	-
40	50	-	± 0,80	-	-	-	-

[a] For seamless hollow profiles the tolerances given for wall thickness *C* shall apply.

Table 8 — Tolerances on wall thickness for profiles with a circumscribing circle over 300 mm – Alloy group II

Dimensions in millimetres

Nominal wall thickness *A*, *B* or *C*		Tolerances on wall thickness					
		Wall thickness *A* Circumscribing circle		Wall thickness *B*[a] Circumscribing circle		Wall thickness *C* Circumscribing circle	
Over	Up to and including	$300 < CD \leq 500$	$500 < CD \leq 800$	$300 < CD \leq 500$	$500 < CD \leq 800$	$300 < CD \leq 500$	$500 < CD \leq 800$
-	1,5	± 0,35	-	-	-	-	-
1,5	3	± 0,45	± 0,50	± 0,70	± 0,90	± 0,90	± 1,2
3	6	± 0,60	± 0,60	± 0,90	±1,0	± 1,2	± 1,3
6	10	± 0,65	± 0,70	± 1,2	± 1,5	± 1,5	± 1,9
10	15	± 0,70	± 0,80	± 1,5	± 1,8	± 1,9	± 2,3
15	20	± 0,75	± 0,85	± 2,0	± 2,5	± 2,5	± 3,1
20	30	± 0,80	± 0,90	± 2,5	± 3,0	± 3,1	± 3,7
30	40	± 0,90	± 1,0	± 3,0	± 3,2	-	-
40	50	± 1,0	± 1,1	-	-	-	-

[a] For seamless hollow profiles the tolerances given for wall thickness *C* shall apply.

3.2 Length

If fixed lengths are to be supplied, this shall be stated on the order. The tolerances on fixed length shall be specified in table 9.

Table 9 — Tolerances on fixed length

Dimensions in millimetres

Circumscribing circle diameter CD		Tolerances on fixed length L				
Over	Up to and including	$L \leq 2\,000$	$2\,000 < L \leq 5\,000$	$5\,000 < L \leq 10\,000$	$10\,000 < L \leq 15\,000$	$15\,000 < L \leq 25\,000$
-	100	$^{+5}_{0}$	$^{+7}_{0}$	$^{+10}_{0}$	$^{+16}_{0}$	$^{+22}_{0}$
100	200	$^{+7}_{0}$	$^{+9}_{0}$	$^{+12}_{0}$	$^{+18}_{0}$	$^{+24}_{0}$
200	450	$^{+8}_{0}$	$^{+11}_{0}$	$^{+14}_{0}$	$^{+20}_{0}$	$^{+28}_{0}$
450	800	$^{+9}_{0}$	$^{+14}_{0}$	$^{+16}_{0}$	$^{+22}_{0}$	$^{+30}_{0}$

If no fixed length is specified in the order, profiles may be delivered in random lengths.

The length range and the tolerances on the random length shall be subject to agreement between purchaser and supplier.

3.3 Squareness of cut ends

The squareness of cut ends shall be within half of the fixed length tolerance range specified in Table 9 for both fixed and random length, e.g. for a fixed length tolerance of $^{+10}_{0}$ mm, the squareness of cut ends shall be within 5 mm.

4 Tolerances on form


4.1 General

Tolerances on form for O and Tx510 tempers shall be subject to agreement between purchaser and supplier.

4.2 Straightness

Deviations from straightness, h_s and h_t, shall be measured as shown in Figure 5 with the profile placed on a horizontal baseplate so that its own mass decreases the deviation.

The straightness tolerance h_t shall not exceed 1,5 mm/m length. Local deviations h_s from straightness shall not exceed 0,6 mm/300 mm length.

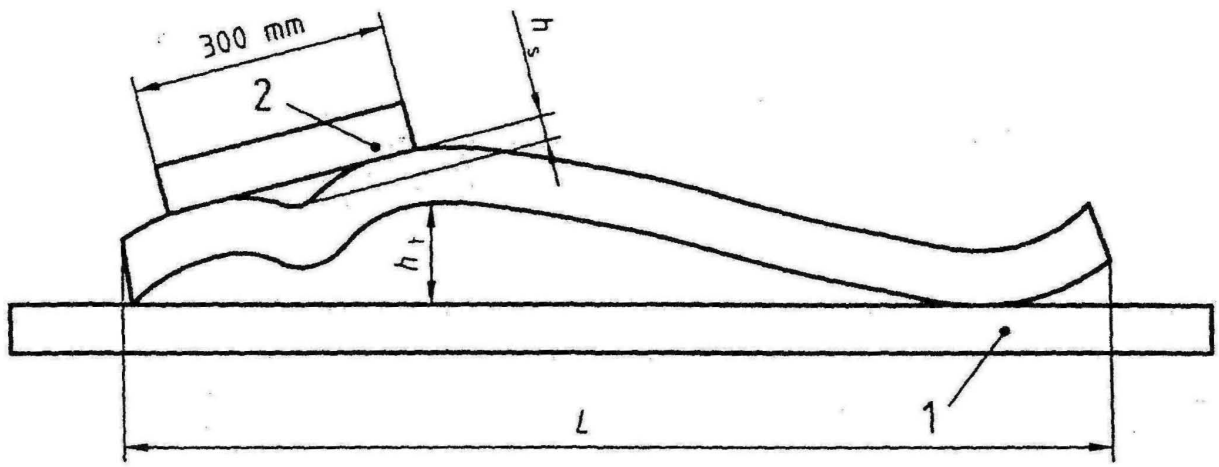


Key

1 Baseplate
2 Ruler

Figure 5 — Measurement of deviation from straightness

4.3 Convexity - Concavity

The convexity - concavity shall be measured as shown in Figure 6. The maximum allowable deviation on convexity - concavity for solid and hollow profiles shall be as specified in Table 10 as a function of profile thickness width W and thickness t.

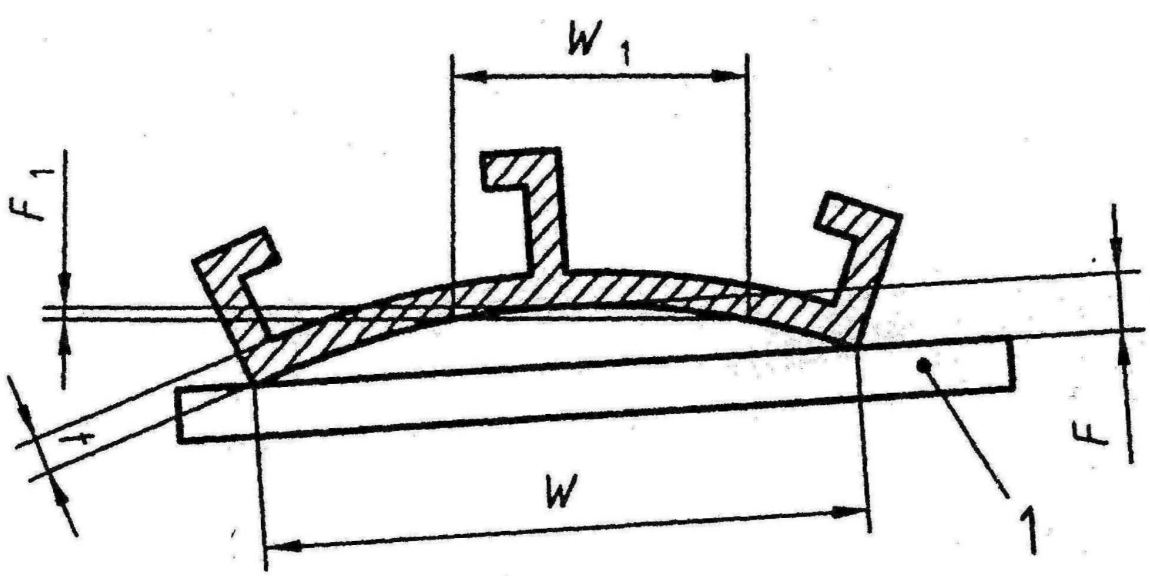

Key

1 Baseplate

Figure 6 — Measurement of convexity - concavity

Table 10 — Convexity - concavity tolerances

Dimensions in millimetres


Width W		Deviation F		
		Hollow profiles [a]		
Over	Up to and including	Wall thickness $t \leq 5$	Wall thickness $t > 5$	Solid profiles
-	30	0,30	0,20	0,20
30	60	0,40	0,30	0,30
60	100	0,60	0,40	0,40
100	150	0,90	0,60	0,60
150	200	1,2	0,80	0,80
200	300	1,8	1,2	1,2
300	400	2,4	1,6	1,6
400	500	3,0	2,0	2,0
500	600	3,6	2,4	2,4
600	800	4,0	3,0	3,0

[a] If the profile has varying wall thicknesses in the measurement range, the thinnest wall thickness shall be used.

In the case of solid and hollow profiles with a width W of least 150 mm, the local deviation F_1, shall not exceed 0,7 mm for any 100 mm of width W_1.

4.4 Contour

For profiles with curved cross sections, the deviation at any point of the curve from the theoretically exact line as defined by the drawing, shall not be greater than the appropriate tolerance C specified in Table 11. Considering all points on the curve, a tolerance zone shall be defined as the zone between two envelopes running tangentially to all circles of diameter C which can be drawn with their centres lying along the theoretically exact line ; this is shown in Figure 7 (a and b).

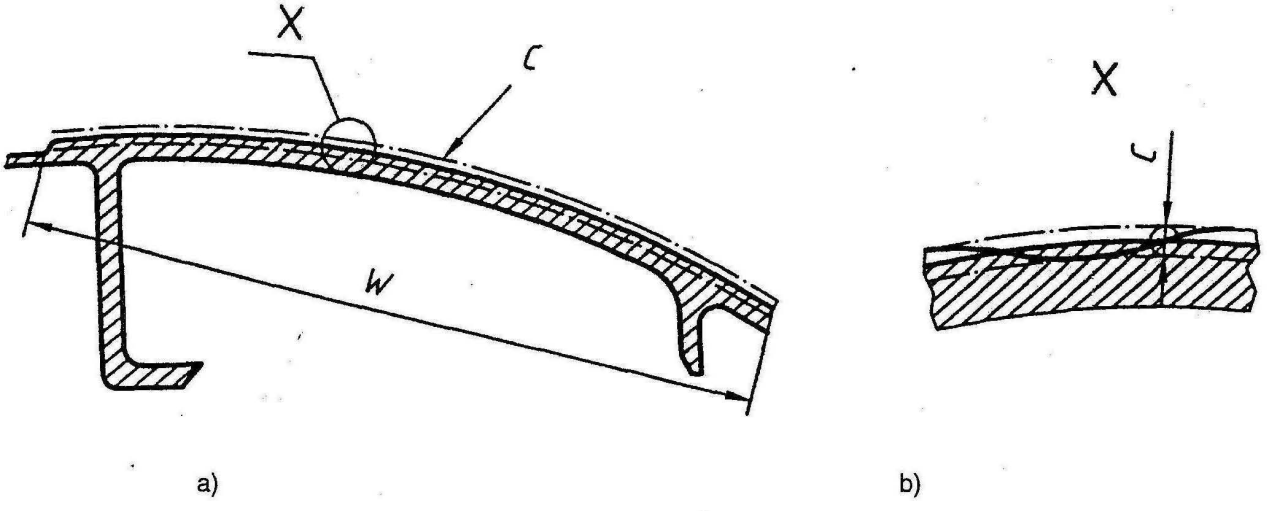

a) b)

Figure 7 — Definition of contour tolerances

Table 11 — Contour tolerances


Dimensions in millimetres

Width W of the contour		Contour tolerance = diameter C of the tolerance circle
Over	Up to and including	
-	30	0,30
30	60	0,50
60	90	0,70
90	120	1,0
120	150	1,2
150	200	1,5
200	250	2,0
250	300	2,5
300	400	3,0
400	500	3,5
500	800	4,0

NOTE Contour tolerances can be checked by placing a section of the profile on a 1:1 scale projection of the drawing with the contour tolerance indicated on the drawing. Another recommended method is the use of suitable gauges (min./max.).

4.5 Twist

Twist T shall be measured as shown in Figure 8 by placing the profile on a flat baseplate the profile resting under own mass, and measuring the maximum distance at any point along the length between the bottom surface of the profile and the baseplate surface. Tolerances shall be as specified in Table 12 as a function of the width W and the length L of the profile.

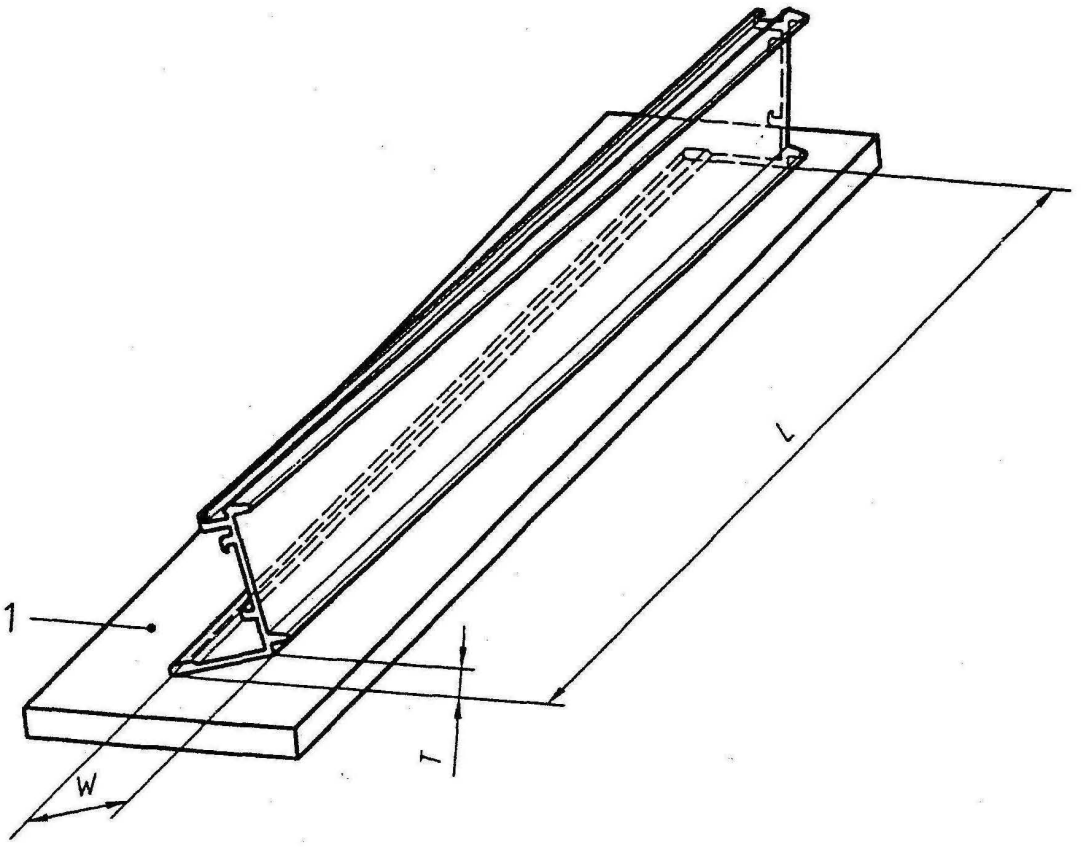

Key

1 Baseplate

Figure 8 — Measurement of twist

Table 12 — Twist tolerances

Dimensions in millimetres

Width W		Twist tolerance T for length L		
			On total profile length L	
Over	Up to and including	Per 1 000 of length[a]	Over 1 000 and including 6 000	Over 6 000
-	30	1,2	2,5	3,0
30	50	1,5	3,0	4,0
50	100	2,0	3,5	5,0
100	200	2,5	5,0	7,0
200	300	2,5	6,0	8,0
300	450	3,0	8,0	1,5 x L (L in metres)
450	600	3,5	9,5	
600	800	4,0	10,0	

[a] Twist tolerances for lengths less than 1 000 mm shall be subject to agreement between purchaser and supplier.

4.6 Angularity

The deviation from a specified angle shall be measured as shown in Figures 9 and 10.

The angularity tolerances for right angles shall be as specified in Table 13 as a function of profile width W.

The maximum allowable deviation α in an angle other than a right angle shall be ± 1°.

In the case of unequal side lengths the tolerance on angularity shall apply to the shorter side of the angle, i.e. it is measured starting from the longer side.

Table 13 — Angularity tolerances for right angles

Dimensions in millimetres

Width W		Maximum allowable deviation, Z from a right angle
Over	Up to and including	
-	30	0,4
30	50	0,7
50	80	1,0
80	120	1,4
120	180	2,0
180	240	2,6
240	300	3,1
300	400	3,5

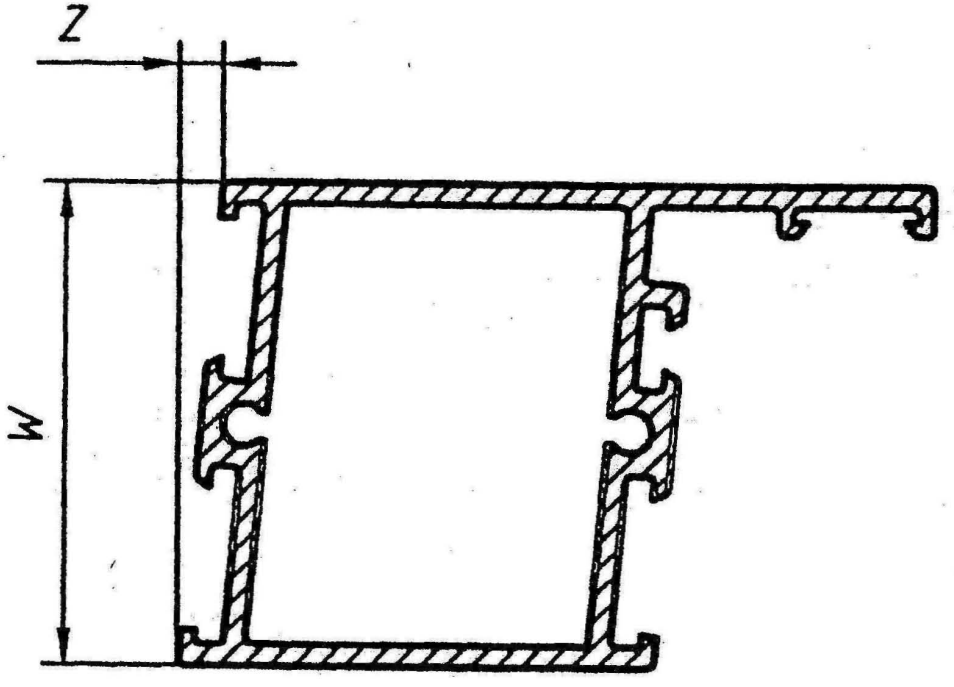


Figure 9 — Measurement of angularity in a right angle

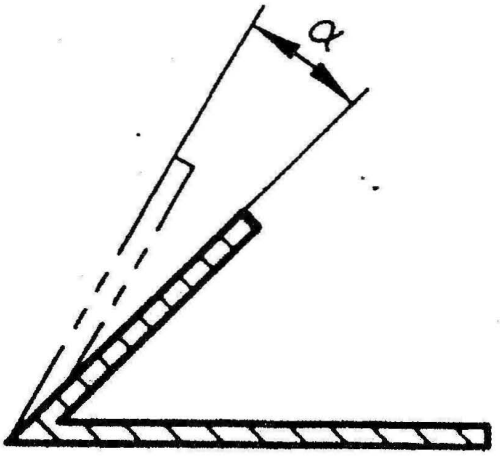


Figure 10 — Measurement of angularity in an angle other than a right angle

4.7 Corner and fillet radii

Sharp corners and fillets may be slightly rounded unless otherwise indicated on the drawing. The maximum allowable corner and fillet radii shall be as specified in Table 14.

When a corner or fillet radius is specified, the maximum allowable deviation from this radius shall be as specified in Table 15.

Table 14 — Maximum allowable corner and fillet radii

Dimensions in millimetres

Wall thickness	Maximum allowable radius	
A, *B* or *C* [a]	Alloy group I	Alloy group II[b]
≤ 5	0,6	0,8
> 5	1,0	1,5

a Where varying wall thicknesses are involved, the maximum allowable radius in the transition zone is a function of the greater wall thickness.

b These tolerances only apply to 6xxx series alloys in group II. The maximum allowable radii for the other alloys in group II shall be subject to agreement between purchaser and supplier.

Table 15 — Maximum allowable deviation from specified corner and fillet radii

Specified radius mm	Maximum allowable deviation from specified radius
≤ 5	± 0,5 mm
> 5	± 10 %